

Antimicrobial Activity of *Coleus ambonicus* Herbal Finish on Cotton Fabric

DOI: 10.5604/01.3001.0010.2854

Bannari Amman Institute of Technology,
Sathyamangalam, Tamil Nadu, India-638401
*E-mail: gokin_m@yahoo.co.in

Abstract

An extract obtained from *Coleus ambonicus* was applied on cotton fabric by means of the exhaust, micro encapsulation and nano encapsulation methods, and the antimicrobial activity of the finished fabric assessed quantitatively by the AATCC test method 100 against gram positive (*Staphylococcus aureus*) and gram negative (*Escherichia coli*) microbes. The finish applied on the samples using all three methods exhibit a good bacterial reduction percentage. The finish applied on the samples using all three methods possesses a higher bacterial reduction percentage against gram positive microbes than gram negative, even after washing. The method of washing conforms to ISO method 3. The wash durability of the antimicrobial activity was assessed by the bacterial reduction percentage after washing. The wash durability of the samples using the direct exhaust method was very poor and it lost its antimicrobial activity after 10 wash cycles. The wash durability of the samples using the micro encapsulated method shows antimicrobial activity up to 10 wash cycles, dropping gradually to very low levels at 20 wash cycles. The wash durability of the samples using nano encapsulation shows good antimicrobial activity against both gram positive and gram negative microbes even after 30 washes.

Key words: *Coleus ambonicus*, cotton, micro encapsulation, nano encapsulation, antimicrobial activity, bacterial reduction %, FTIR spectrum, wash durability.

Introduction

Natural textile fibres like cotton are prone to microbe growth. The moisture regain of cotton, the climate conditions in India and the cellulose present in cotton favour microbe growth [1, 2]. Microbial growth on textiles may cause foul smells, skin irritation, cross infection, discolouration and colour stain. It also affects the functional properties of fabric like strength and elastic properties [3].

A wide range of synthetic antimicrobial agents like triclosan, metals and their salts, organometallics, phenols and quaternary ammonium compounds have been applied to cotton [4]. Synthetic antimicrobial agents have excellent antimicrobial efficacy for a wide range of microbes, but issues of eco-friendliness & biodegradability limit the use of synthetic antimicrobial agents [5]. Natural antimicrobial agents like neem, pomegranate fruit, tulsi leaf and etc., possess very good resistance to most microbes [6-10]. Most of the natural antimicrobial agents are available in abundance and are eco-friendly.

The encapsulation process increases the life cycle of the finish by a controlled

release mechanism. The nano encapsulation method of finishing provides a high surface area and extends the shelf-life of the finish on cotton [11, 12].

Coleus ambonicus is a medicinal plant found abundantly in India. Six major compounds account for 97% of the composition of the *Coleus ambonicus* extract. Of these six, thymol is the major compound and has antimicrobial, antifungal and insecticidal properties [13]. The other flavonoid and phenol functional groups present in the herbal extract may also contribute to antimicrobial activity [14]. In this work, the antimicrobial activity of *Coleus ambonicus* herbal finish on cotton fabrics was analysed using the direct, micro encapsulation and nano encapsulation methods.

Materials and methods

Materials

In my study, 100% cotton fabric with a plain weave construction was used. The fabric has 32 threads per centimeter in the warp and weft directions. The yarn count used for this purpose was 15 tex in the warp and weft directions. 115 grams per square meter fabric density was used. The fabric was desized, scoured and bleached with the standard recipe.

Coleus ambonicus used as natural antimicrobial agents was collected locally from the Sathyamangalam village, Erode district, Tamil Nadu, India.

Preparation of herbal *Coleus ambonicus* extract

Collected *Coleus ambonicus* herbal leaves were shade dried to reduce the moisture content of the leaf to below 10%. Unwanted materials like dirt and other parts of plants were removed manually by hand. The dried herbal leaves were crushed into small pieces and made into powder, using a mixer. The ground herbal powder was then sieved using fine mesh fabric to remove unground portions. 20 grams of the fine herbal powder was refluxed in a Soxhlet apparatus (Borosil, India) in 200 ml of methanol. The resultant supernatant was filtered with Whatman No.1 filter paper and the filtrate was maintained at room temperature to remove organic solvents. The fabric to be treated with the herbal extract was scoured with soap at 60 °C to remove any existing surface finish. The soap treated fabric was washed with distilled water and air dried. The herbal extract prepared was applied to the cotton fabric using the exhaust method with a 1:30 material to liquor ratio at 60 °C for 30 minutes, after which the fabric was washed and dried in air.

Micro encapsulation of herbal extract

Gum acacia was taken as wall material for encapsulation of the *Coleus ambonicus* extract. 10 grams of gum acacia was allowed to swell for half an hour by mixing with 100 ml of hot water. 50 ml of hot water was added to this mixture and stirred for 15 minutes at 40 °C to 50 °C

temperature. 10 ml of core material *Coleus ambonicus* was added to this mixture and stirred at 300-500 rpm for 15 minutes. 10 ml of 20% sodium sulphate solution was added slowly drop wise for 5-10 minutes. 5 ml of 17% formaldehyde was added at a slower stirrer speed. The stirrer was then stopped and the mixture was freeze dried. The cotton fabric was immersed in the micro encapsulated herbal extract using the exhaust method with a 1:20 material to liquor ratio at 55 °C for 30 minutes and then dried at 80-85 °C in an oven.

Nano encapsulation of herbal extract

The herbal extract prepared was encapsulated with bovine serum albumin as the wall material by the coacervation process, followed by cross linking with glutaraldehyde. The *Coleus ambonicus* herbal extract was incubated for an hour at room temperature with the 2% bovine serum albumin protein powder required. A digital pH meter was used to adjust the pH to 5.5, by means of a 0.1M HCL. Ethanol was added slowly at 1 ml per minute into the solution to obtain a 2:1 ratio (v/v). The required amount of 25% glutaraldehyde was added and kept for two hours to allow the cross linking of protein. A rotary vacuum evaporator was used at reduced pressure to remove organic solvents. The resultant nano particles were purified by centrifuging at 4 °C and 10,000 rpm. The resulting pellets formed of nano capsules were suspended in a phosphate buffer (pH: 7.4, 0.1M) and lyophilised with 2% w/v mannitol. The nano capsules thus obtained were further dried by lyophilisation. The resultant nano encapsulated herbal powder was applied on cotton by the exhaust method. Citric acid was used as a binder with a 1:20 material-to-liquor ratio at 55 °C temperature for 30 minutes. Antimicrobial activity of the finished fabric was assessed by the AATCC 100 test method.

Test methods

Antimicrobial activity of the treated and untreated samples was assessed quantitatively by the agar diffusion test method (AATCC 100). 4.8 ± 0.1 cm circular cut treated, untreated and control samples were inoculated with the required quantity of AATCC specified gram positive (*Staphylococcus aureus*) and gram negative (*Escherichia coli*) test organisms. 100 ± 1 ml of neutralising solution distilled water was added and incubated at

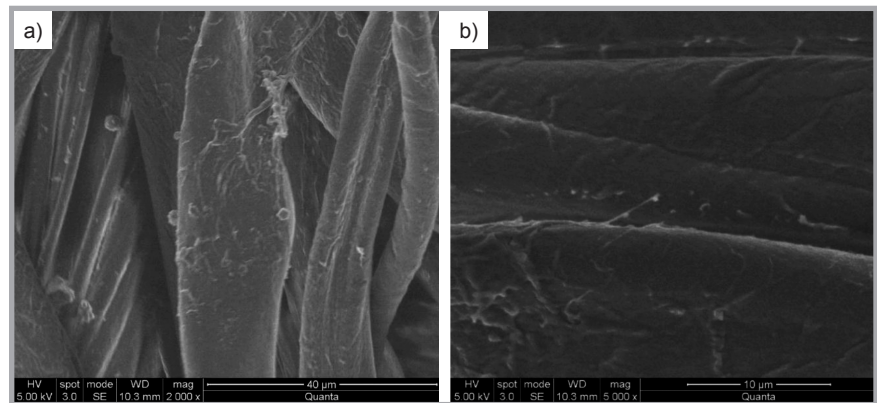


Figure 1. SEM photographs of fabric treated with nano encapsulated *Coleus Ambonicus* at magnifications: a) 2000, b) 5000.

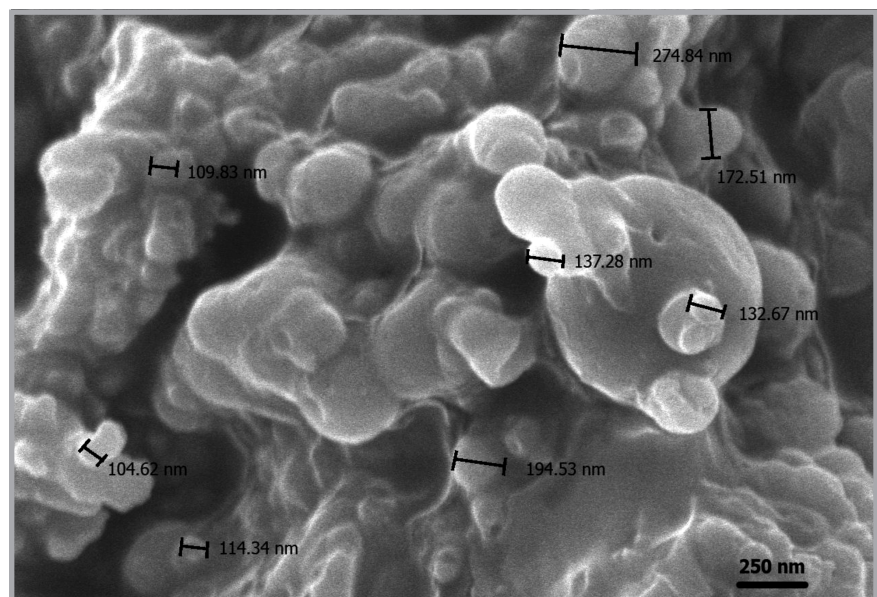


Figure 2. Particle size of nano encapsulated *Coleus Ambonicus* herbal powder.

37 ± 2 °C for 24 hours. After incubation, the number of bacteria present in the solution and percentage reduction (R) were calculated using the following formula:

$$R = 100(B-A)/B$$

Where, A is the number of bacteria recovered from inoculated treated test specimen swatches in a jar incubated over the contact period desired, and B the number of bacteria recovered from inoculated treated test specimen swatches in a jar immediately after inoculation (AATCC test method). The durability of the finishing was assessed by analysing antimicrobial activity of the washed samples. The washing of the sample was done in a laundrometer with the ISO 3 wash test method. After the specified number of washes, the test samples were taken and washed thoroughly for further

assessment. A scanning electron microscope was used to analyse the binding of nano encapsulated particles on the fabric. An FTIR8400S Spectrophotometer (Shimadzu, Japan) was used to obtain FTIR spectra to discover functional groups present in the sample.

Result and discussion

SEM analysis

Figure 1 shows SEM photographs of nano encapsulated *Coleus ambonicus* at different magnifications. It is clear that the nano encapsulated *Coleus ambonicus* was attached to the fibre surface firmly.

Figure 2 shows the diameter of the nano encapsulated powder. The average diameter of the nano encapsulated powder is around 155.07 nm.

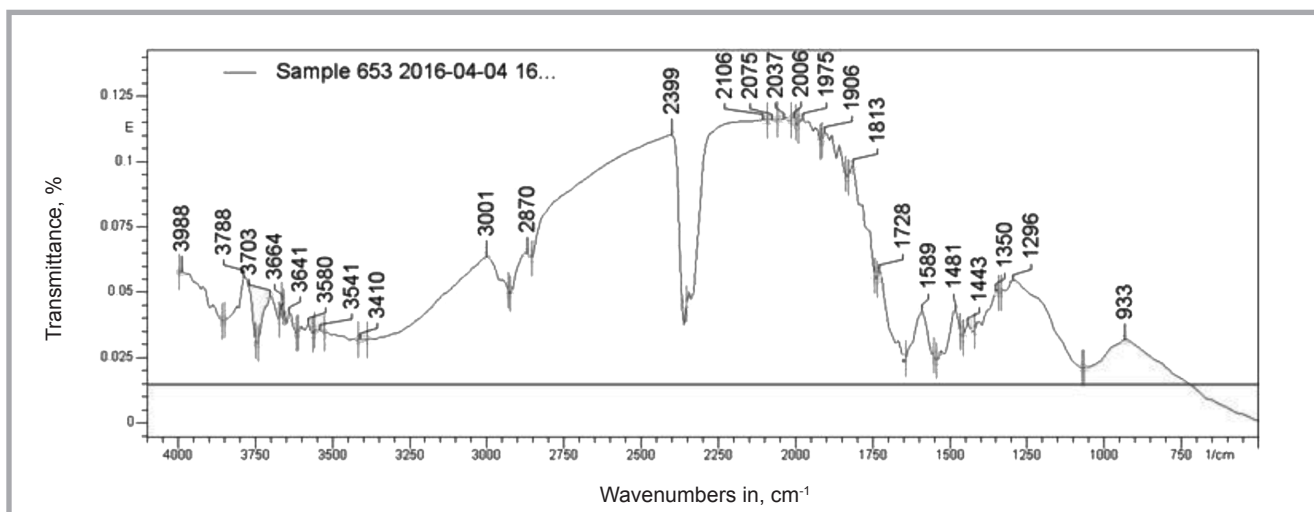


Figure 3. FTIR analysis of *Coleus ambonicus*.

FTIR spectrum analysis

The peaks in the FTIR spectrum confirm functional groups present in the herbal powder. Figure 3 shows the FTIR spectrum obtained from the *Coleus ambonicus* herbal extract. The peaks 1580-1590 cm^{-1} substantiate the presence of primary alkyl amide, 3600-3700 cm^{-1} – the existence of O-H phenolic compounds, and 3000-2900 cm^{-1} revealed the presence of C-H in the aromatic phenolic functional groups. Peaks at 2000-2200 cm^{-1} confirm the presence of flavonoids [15]. The presence of flavonoids provides the natural colour of the herbal extract and antimicrobial properties [16]. The existence of these functional groups in *Coleus ambonicus* is responsible for the antimicrobial activity of the sample.

Antimicrobial activity

The bacterial reduction percentage of the sample finished using the direct exhaust method, micro encapsulation method and nano encapsulation method was assessed

quantitatively by the AATCC agar diffusion test method 100, the results of which are given in Table 1. The samples finished with *Coleus ambonicus* in all three methods show good antimicrobial activity. This may be due to the rich content of thymol in *Coleus ambonicus* herbs. Sivropoulou A et al. reported the antimicrobial activity of *Coleus ambonicus* due to the presence of thymol [13] and consolacion. Y. Ragasa et al. reported three flavones: *salvigenin*, *cirsimaritin* and *chrysoeriol* present in *Coleus ambonicus* herbs and that the presence of these flavones contributes to the antimicrobial activity of the herbs [14].

The samples finished by the direct exhaust method show a better degree of bacterial reduction percentage for both gram positive (*Staphylococcus aureus*) and gram negative (*Escherichia coli*) than the micro encapsulation and nano encapsulation methods before washing. The samples finished by the direct exhaust, micro encapsulation and nano

encapsulation methods possess a higher bacterial reduction percentage against gram positive microbes than gram negative. This indicates that *Coleus ambonicus* herbs are very active against gram positive rather than against gram negative.

Wash durability of finishing

Table 2. show the wash durability of the samples finished by the direct, micro encapsulation and nano encapsulation methods. A marked reduction in the bacterial reduction percentage was observed in the sample finished by the direct exhaust method when increasing the wash cycles. The bacterial reduction percentage was 15 and 12 for *S. aureus* and *E. coli*, respectively, after 10 wash cycles, confirming that the direct method of application has poor wash durability of finishing.

The micro and nano encapsulated samples show better resistivity in both gram positive and gram negative microbes than for the direct method after washing. It is evident that the nano encapsulated and micro encapsulated samples have restricted release of anti microbial agents.

The samples finished by the micro encapsulation method exhibit good resistance to both gram positive and gram negative

Table 1. Bacterial reduction percentage of the sample at zero wash cycles.

| | Zero wash | |
|---------------------|------------------|----------------|
| | <i>S. aureus</i> | <i>E. coli</i> |
| Direct method | 100 | 100 |
| Micro encapsulation | 87 | 82 |
| Nano encapsulation | 85 | 81 |

Table 2. Bacterial reduction percentage of samples at different wash cycle.

| | Zero wash | | 5 wash | | 10 wash | | 20 wash | | 30 wash | |
|---------------------|------------------|----------------|------------------|----------------|------------------|----------------|------------------|----------------|------------------|----------------|
| | <i>S. aureus</i> | <i>E. coli</i> | <i>S. aureus</i> | <i>E. coli</i> | <i>S. aureus</i> | <i>E. coli</i> | <i>S. aureus</i> | <i>E. coli</i> | <i>S. aureus</i> | <i>E. coli</i> |
| Direct method | 100 | 100 | 56 | 51 | 15 | 12 | 0 | 0 | 0 | 0 |
| Micro encapsulation | 87 | 82 | 78 | 73 | 65 | 58 | 18 | 11 | 0 | 0 |
| Nano encapsulation | 85 | 81 | 80 | 76 | 75 | 71 | 58 | 54 | 38 | 31 |

microbes up to 10 wash cycles. After that, the antimicrobial activity deteriorated, was very low at 20 wash cycles and with no activity at 30 wash cycles. It is also evident that the micro-encapsulated samples exhibit good resistivity against both gram positive and gram negative microbes up to 10 wash cycles, which dropped at 20 wash cycles [17].

The nano encapsulated method displays good antimicrobial activity in terms of bacterial reduction percentage up to 20 wash cycles and shows moderate antimicrobial activity after 30 wash cycles, with both gram positive and gram negative microbes. It reveals that the nano encapsulated sample exhibits good wash durability in comparison to the micro encapsulation and direct exhaust methods.

Conclusions

Coleus Amboenicus finished fabric samples show good microbial reduction percentage in both *staphylococcus aureus* and *Escherichia coli* microbes in all three methods at zero washes. The nano encapsulated fabric sample exhibits good wash durability in terms of the bacterial reduction percentage even after 30 wash cycles, whereas the direct method and micro encapsulated method of finishing showed less durability after 10 and 20 wash cycles, respectively.



References

- Vidushi Bajpai, Shailendra Bajpai, Jha M K, Apurba Dey, Subrata Ghosh. Microbial Adherence on Textile Materials: A Review. *Journal of Environmental Research and Development* 2011; 5, 3.
- Boryo DEA. The Effect of Microbes on Textile Material: A Review on the Way-Out So Far. *The International Journal of Engineering and Science (IJES)* 2013; 2, 8: 09-13.
- Fulekar M H, Shrutika LWadgaonkar, Anamika Singh. Decolourization of Dye Compounds by Selected Bacterial Strains isolated from Dyestuff Industrial Area. *International Journal of Advancements in Research & Technology* 2013; 2, 7, ISSN 2278-7763.
- Yuan Gao, Robin Cranston. Recent Advances in Antimicrobial Treatments of Textiles. *Textile Research Journal* 2008; 78, 1: 60-72.
- Roman Jantas, Katarzyna Górna. Antibacterial Finishing of Cotton Fabrics. *Fibres and Textiles in Eastern Europe* 2006; 14, 1(55): 88-91.
- Sathianarayanan M P, Bhat N V, Kokate S S, Walunj V E. Antibacterial finish for cotton fabric from herbal Products. *Indian Journal of Fibre and Textile Research* 2010; 35: 50-58.
- Joshi M, Wazed Ali S, Purwar R. Ecofriendly antimicrobial finishing of textiles using bioactive agents based on natural products. *Indian Journal of Fibre and Textile Research* 2009; 34: 295-304.
- Dierk Knittel, Eckhard Schollmeyer. Chitosans for Permanent Antimicrobial Finish on Textiles. *Lenzinger Berichte* 2006; 85: 124-130.
- Yong-Sik Chung, Kwang-Keun Lee and Jin-Woo Kim. Durable Press and Antimicrobial Finishing of Cotton Fabrics with a Citric Acid and Chitosan Treatment. *Textile Research Journal* 1998; 68, 10: 772-775.
- Weijun Ye, John H. Xin, Pei Li, Kam-Len Daniel Lee, Tsz-Leung Kwong. Durable Antibacterial Finish on Cotton Fabric by Using Chitosan-Based Polymeric Core-Shell Particles. *Journal of Applied Polymer Science* 2006; 102: 1787-1793.
- Mohanraj S, Vanathi P, Sowbarniga N, Saravanan D. Antimicrobial effectiveness of Vitex negundo leaf extracts. *Indian Journal of Fibre and Textile Research* 2012, 37, 12: 389-392.
- Sumithra M, Vasugi Raaja N. Micro-encapsulation and nano-encapsulation of denim fabrics with herbal extracts. *Indian Journal of Fibre and Textile Research* 2012; 37, 12: 321-325.
- Gurdip Singh, Om Prakash Singh, Prasad Y R, de Lampasona M P, Catalan C. Studies on essential oils, Part 33: chemical and insecticidal investigations on leaf oil of *Coleus amboenicus* Lour. *Flavour Fragr. J.* 2002; 17: 440-442.
- Consolacion Y, Ragasa Zeus Pendon, Veronica Sangalang, John A. Rideout. Antimicrobial flavones from *coleus amboenicus*. *Philippine Journal of Science* 1999; December 128(4) : 347-351.
- Joseph B, Lambert et al. Introduction to Organic Spectroscopy, Macmillan Publications 1987; p.171-176.
- Tim Cushnie TP, Andrew J Lamb. Antimicrobial Activity of Flavonoids. *International Journal of Antimicrobial Agents* 2005; 26: 343-356.
- Thilagavathi G, Krishna Bala S. Micro-encapsulation of herbal extracts for microbial resistance in healthcare textiles. *IJFTR* 2007; 32, September: 351-354.
- Zulfiker A H M, Roy PP, MAM Momin, Khan M S, Bulbul IJ, Tahmed Rana M S. Investigation of antioxidant and antimicrobial potential of chloroform and petroleum ether extracts of selected medicinal plants of Bangladesh. *British Journal of Medicine & Medical Research* 2013; 3(4): 1418-1436.
- Sathianarayanan MP, Chaudhari BM, Bhat NV. Development of durable antimicrobial agent from ban-ajwain seed (*Thymus serpyllum*) for cotton fabric. *IJFTR* 2011; 36, September: 234-241.

Received 29.11.2016 Reviewed 20.03.2017

Institute of Textile Engineering and Polymer Materials



The Institute of Textile Engineering and Polymer Materials is part of the Faculty of Materials and Environmental Sciences at the University of Bielsko-Biala. The major task of the institute is to conduct research and development in the field of fibers, textiles and polymer composites with regard to manufacturing, modification, characterisation and processing.

The Institute of Textile Engineering and Polymer Materials has a variety of instrumentation necessary for research, development and testing in the textile and fibre field, with the expertise in the following scientific methods:

- FTIR (including mapping),
- Wide Angle X-Ray Scattering,
- Small Angle X-Ray Scattering,
- SEM (Scanning Electron Microscopy),
- Thermal Analysis (DSC, TGA)

Strong impact on research and development on geotextiles and geosynthetics make the Institute of Textile Engineering and Polymer Materials unique among the other textile institutions in Poland.

Contact:

Institute of Textile Engineering and Polymer Materials
University of Bielsko-Biala
Willowa 2, 43-309 Bielsko-Biala, POLAND
+48 33 8279114,
e-mail: itimp@ath.bielsko.pl
www.itimp.ath.bielsko.pl



INSTITUTE OF BIOPOLYMERS AND CHEMICAL FIBRES INSTYTUT BIOPOLIMERÓW I WŁÓKIEN CHEMICZNYCH



Director of the Institute: Danuta Ciechańska Ph.D., Eng.

The Institute of Biopolymers and Chemical Fibres was consolidated with the Pulp and Paper Research Institute in 2007.

The research subject of IBWCH is conducting scientific and development research, as well as implementing their results into praxis in the following fields:

- processing, modifying, and application of biopolymers,
- techniques and technologies of manufacturing, processing, and application of chemical fibres and other polymer materials and related products,
- techniques and technologies connected with manufacturing, processing and application of products of the pulp and paper industry and related branches

R&D activity includes the following positions, among others:

- biopolymers – modifying and processing,
- functional, thermoplastic polymers,
- biodegradable polymers and products from recovered wastes,
- industrial biotechnology, e.g. bioprocesses for modifying and processing polymers and fibres, and biosyntheses of nanobiomaterial polymers,
- biomaterials for medicine, agriculture, and technique,
- nano-technologies, e.g. nano-fibres, polymer nano-coatings, nano-additives for fibres.
- processing of polymer materials into fibres, films, micro-, and nano- fibrous forms, and nonwovens,
- paper techniques, new raw material sources for manufacturing paper pulps,
- environmental protection,

The Institute is active in implementing its works in the textile industry, medicine, agriculture, plastic processing, filter and packing materials manufacturing, as well as in the cellulose and paper industries.

The Institute has the following five laboratories, which have accreditation certificates PCA:

- Laboratory of Microbiology
- Laboratory of Biodegradation
- Laboratory of Environment Protection
- Laboratory of Metrology
- Laboratory of Paper Quality

The Institute's offer of specific services is wide and differentiated, and includes:

- physical, chemical and biochemical investigations of biopolymers and synthetic polymers,
- physical, including mechanical investigation of fibres, threads, textiles, and medical products,
- tests of antibacterial and antifungal activity of fibres and textiles,
- investigation in biodegradation,
- investigation of morphological structures by SEM and ESEM
- investigation and quality estimation of fibrous pulps, card boards, and paper products, including paper dedicated to contact with food, UE 94/62/EC tests, among others.
- Certification of paper products.

The Institute is member of domestic and international scientific organisations, the following, among others: EPNOE Association-European Polysaccharide Network of Excellence, Polish Chitin Society, Centre of Advanced Technology of Human-Friendly Textiles 'PROHUMANOTEX', Polish Platform of Textile Technology, Polish Platform of the Forest-Wood Technology Sector, International Scientific Network 'Environment versus Technology' ENVITECH-NET.

The Institute participates in the following strategic research projects: KEY PROJECT: 'Biodegradable fibrous goods', BI-OGRATEX – PO IG 01.03.01-00-007/08; FORESIGHT PROJECT: 'Modern technologies for textile industry. A Chance for Poland' – UDA – PO IG 01.01.01-00-005/09-00 (as a leader); STRATEGIC PROJECT: 'Technology for the preparing of biodegradable polyesters using renewable raw materials', BIOPOL – PO IG 01.01.02-10-025/09; STRATEGIC PROJECT: 'Application of biomass for production of environmentally friendly polymeric materials', BIOMASS – PO IG 01.01.02-10-123/09.

The Institute organises educational courses and workshops in fields related to its activity.

The Institute is active in international cooperation with a number of corporation, associations, universities, research & development institutes, and companies from Austria, Germany, Finland, France, Sweden and the United States among others.

The Institute is publisher of the scientific journal 'Fibres & Textiles in Eastern Europe'; the journal is since 1999 on the 'Philadelphia List' of the Institute for Scientific Information.

Instytut Biopolimerów i Włókien Chemicznych (IBWCh)

Institute of Biopolymers and Chemical Fibres

ul. Skłodowskiej-Curie 19/27, 90-570 Łódź, Poland;

Phone: (48-42) 638-03-02, Fax: (48-42) 637-65-01, E-mail: ibwch@ibwch.lodz.pl <http://www.ibwch.lodz.pl>



INNOVATIVE ECONOMY
NATIONAL COHESION STRATEGY

EUROPEAN UNION
EUROPEAN REGIONAL
DEVELOPMENT FUND

